



**EOS/ESD Association Services, LLC**

# Product Test Report

Bertech Nitrile Gloves

Model: NPF-9 Series

Testing per:

ANSI/ESD STM15.1-2019

Technician - Brennan Pimpinella

*The results provided in this report are accurate within the limits appropriate to each test standard. This report shall not be reproduced, except in full, without written permission from EOS/ESD Association Services, LLC.*

Bertech white gloves were tested per ANSI/ESD STM15.1-2019 using a CAFÉ probe fixture.

Test Date: 2/06/26

Test Facility: EOS/ESD Association Services LLC

Conditioning Temperature: 23°C

Conditioning Humidity: 12% R.H.

Conditioning Time: 48 hours

Test Temperature: 23°C

Test Humidity: 10%R.H.


Operator: Brennan Pimpinella

Equipment: PRS-801B Resistance System

## Equipment Verification

Upper Resistance	Electrification period in seconds	Test Voltage
1.38E+14	20	100

## Schematic of test points

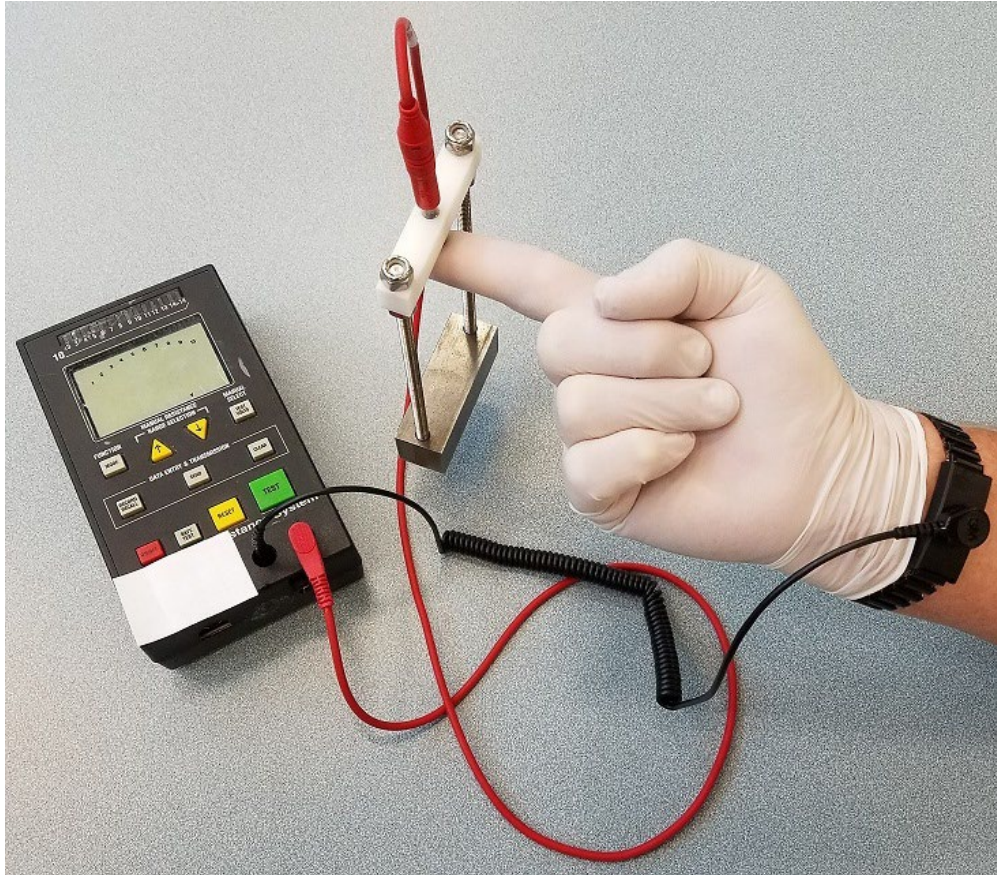

Glove Type: Right Hand Test Voltage: 100

Glove #	Glove 1	Glove 2	Glove 3	Glove 4	Glove 5	Glove 6
Thump	8.98E+08	1.52E+09	1.25E+09	5.63E+08	7.67E+08	2.32E+08
Finger 1	8.73E+08	1.53E+09	1.52E+09	7.32E+08	7.16E+08	1.56E+08
Finger 2	8.89E+08	1.45E+09	1.40E+09	6.17E+08	5.84E+08	8.56E+07
Finger 3	1.04E+09	1.91E+09	1.24E+09	7.02E+08	6.12E+08	8.17E+07
Finger 4	1.05E+09	1.47E+09	1.07E+09	5.05E+08	6.14E+08	5.79E+07
Average	9.47E+08	1.58E+09	1.30E+09	6.24E+08	6.59E+08	1.23E+08
Std. Dev.	4.50E+08	1.90E+08	1.71E+08	9.44E+07	7.87E+07	7.13E+07
Minimum	3.42E+08	1.45E+09	1.07E+09	5.05E+08	5.84E+08	5.79E+07
Maximum	1.52E+09	1.91E+09	1.52E+09	7.32E+08	7.67E+08	2.32E+08

Glove Type: Left Hand Test Voltage: \_\_\_\_\_

Glove #	Glove 1	Glove 2	Glove 3	Glove 4	Glove 5	Glove 6
Thumb	7.56E+08	1.22E+09	5.96E+08	4.47E+08	6.72E+08	5.79E+07
Finger 1	8.15E+08	9.73E+08	7.64E+08	5.42E+08	5.84E+08	1.23E+08
Finger 2	8.89E+08	1.25E+09	8.35E+08	5.46E+08	5.19E+08	8.68E+07
Finger 3	8.85E+08	1.45E+09	7.24E+08	5.00E+08	5.04E+08	1.99E+08
Finger 4	8.49E+08	1.43E+09	5.41E+08	4.36E+08	4.72E+08	1.35E+08
Average	8.39E+08	1.26E+09	6.92E+08	4.94E+08	5.50E+08	1.20E+08
Std. Dev.	5.52E+07	1.93E+08	1.21E+08	5.15E+07	7.94E+07	5.35E+07
Minimum	7.56E+08	9.73E+08	5.41E+08	4.36E+08	4.72E+08	5.79E+07
Maximum	8.89E+08	1.45E+09	8.35E+08	5.46E+08	6.72E+08	1.99E+08

Data Summary for All Fingers:

Average	8.94E+08	Minimum	4.36E+08
Std. Dev.	3.70E+08	Maximum	1.91E+09

*The results provided in this report are accurate within the limits appropriate to each test standard. This report shall not be reproduced, except in full, without written permission from EOS/ESD Association Services, LLC.*

02/06/2026

EOS/ESD Association Services, LLC  
 218 W. Court Street  
 Rome, NY 13440

Submitted to Client by:



Lisa Pimpinella  
 Executive Director